



RESEARCH OF OBTAINING HIGH-QUALITY NITROGEN-PHOSPHORIC FERTILIZERS

Sayfiddinov Osimkhan

Student of Namangan Institute of Engineering and Construction

Tel: +99(891) 356 56 42

e-mail: dcos1mxon@gmail.com

<https://doi.org/10.5281/zenodo.13639492>

ARTICLE INFO

Received: 26th August 2024

Accepted: 30th August 2024

Online: 31th August 2024

KEYWORDS

Phosphoric acid, extraction phosphoric acid, fertilizer, mineral fertilizer, non-fluorinated fertilizer, complex fertilizer, nitrogen-phosphorus fertilizer, ammonium phosphates, monoammonium phosphate, diammonium phosphate.

ABSTRACT

Objective. The aim of the research is the removal of phosphoric acid from Central Kyzylkum phosphates by fluoride and sulphate additives during the extraction of phosphoric acid, iron and aluminium, calcium, magnesium, sulphate, fluorine during the ammonium phosphate acid extraction phase. Study the process of producing environmentally friendly and fully water-soluble ammonium phosphates.

Methods. The study used chemical, physico-chemical (photocolorimetric, pH-metric, electron-microscopic) and statistical processing of experimental data.

Results. The continuation of the phosphoric acid extraction process simplifies the process by removing fluorine and sulphate additives, by deep cleaning of iron and aluminium, calcium, magnesium, fluorine and other additives in the produced acid, the main nutrient element in the finished product - P_2O_5 has been achieved.

Introduction. Currently, the global demand for phosphate raw material is 190 million tonnes or 43 million tonnes of P_2O_5 per year. By 2030, demand for phosphate raw materials is projected to increase to 2 million tons. By 2050, the demand for raw materials will reach 220 million tonnes of phosphate, or 70 million tonnes of P_2O_5 [1].

As a result of large-scale concrete activities in the country, high results have been achieved in scientific research in the production of new types of phosphorus fertilizers based on local raw materials and in the provision of high-quality mineral fertilizers to agriculture.

In the third direction of the Strategy for Action of the Republic of Uzbekistan for 2017-2021 «... accelerated development of high-tech processing industries, primarily production of finished products with high value added based on deep processing of local raw materials. » Important tasks have been identified [2]. In this regard, it is important to create a technology for the production of high quality ammonium phosphates that meet the requirements of drip and hydroponic irrigation.

Therefore, the removal of fluorine and other additives from the product plays a special role in the process. Because fluorine compounds are very harmful to the environment. Research



shows that fluorine not only affects plants but also causes many serious diseases in humans and other organisms.

The recovery and use of fluorine from phosphate feedstock solve two problems: increasing the production of fluorine compounds and preventing damage to the biosphere due to the release of fluorine into the environment. Some of the fluorine from the phosphate feedstock is extracted during extraction and the rest is removed by evaporation, granulation and drying. Phosphate extraction is also achieved by neutralizing phosphoric acid with non-fluoric containing components to reduce the relative fraction of fluorine in the product [3, 4, 5].

Many plants absorb large amounts of fluorine. For example, 1 kg of tea contains between 57 and 1,370 mg of fluorine and 4,500 mg [6, 7]. In this process, fluoride accumulates in the seeds of cotton, and most of it becomes cotton oil. Studies show that the content of fluoride in soil increases when fluorine is added to the soil, including mineral fertilizers [8]. In the presence of nitrogen phosphorus potassium fertilizers, the amount of fluorine absorbed by plants increases [9].

Phosphorus fertilizers are the main source of fluorine in soil. For example, apatite and phosphate contain, on average, 3.0% and 2.7% fluoride, respectively. The extracted phosphate acid (EPA) based on phosphate Central Kyzylkum contains about 1.2% fluoride. The method of deposition of acids from alkali metals in the form of silicon fluoride is not very effective as EPA contains almost very small amounts of acid-soluble silicon compounds [10].

When processing natural phosphates, the fluorine contained therein is distributed between the gas, liquid (EPA) and solid (phosphogypse) phases. According to the dihydrate scheme, 80-85% of the phosphoric acid in the raw material (apatite and phosphate) is converted into a hydrofluoric acid, and after processing into fertilizers.

Increasing the production of phosphorus, especially complex fertilizers, to fully meet the demand for agricultural fertilizers creates a risk of fluorine saturation of soils, plants and water bodies [11]. The negative effects of fluorine compounds entering the atmosphere and open water bodies and accumulating in living organisms and flora have been sufficiently studied [8, 9].

Sulphates, chlorides, phosphates, carbonates and sodium and potassium hydroxides are used to precipitate EPA fluorides as compounds of silicon fluoride of insoluble alkali metals. These methods are based on the chemical interaction of the above-mentioned salts with silica in EPA. Fluorine clearance is up to 90%.

The process of purifying EPAs based on Central Kyzylkum phosphate with alkali metal salts is well described in the literature. EPA is first purified from sulphates and then from fluorine.

The authors have studied in detail the process of fluoridation of EPA based on phosphate Central Kyzylkum sulphate, dihydrophosphate, sodium metasilicate and have shown that the degree of fluoridation can be increased from 38-40% to 80-85% and EPA. Desorption technology developed.

There are also materials for desulphurization of defluorinated EPAs by unprocessed raw materials of the Central Kyzylkum, carbonate and calcium oxide washed with enriched phosphate. A patent has been obtained for obtaining nutrient sediments by purifying EPA of



fluorine and sulphate compounds. However, there are no materials for simultaneous removal of fluoride and sulphate from the extraction pulp when EPA is extracted from the phosphate of the Central Kyzylkum.

Methods. The simultaneous purification of EPA from fluorine and sulphate results in, first, an environmentally friendly product, second, a high contribution of useful substances to the product, third, some coverage of low-grade raw materials, fourth, fluorine - valuable raw materials, joins can be isolated in the process itself. Therefore, research on simultaneously purifying EPA from fluoride and sulphate is relevant.

In order to purify fluorine and other additives in the extracted phosphoric acid and to produce high-quality ammonium phosphates, purification processes for the extraction of phosphoric acid and the neutralization of purified acid with gaseous ammonia were studied.

In the composition for the study, in% by weight: $P_2O_5 = 26,20$; $CO_2 = 3,08$; $CaO = 57,64$; $MgO = 1,07$; $R_2O_3 = 0,79$; $SO_3 = 2,18$; $F = 2,88$; e.v. = 1.54 The washed phosphate concentrate of the Central Kyzylkum (WRPC) is used.

Deposition of fluorine and sulphate from Calcium Carbonate extraction sludge at 60-150% of the calcium oxide fluoride norm and 80-100% of the SO_3 binding norm as calcium sulphate (limestone etc.)) and conducted by WRPC. The process of extraction of phosphoric acid with sulphuric acid was carried out in dihydrate mode, before filtration of the resultant extraction pulp fluorine and free sulphuric acid in it were deposited with calcium carbonate or WRPC.


Ammonia with gaseous ammonia up to pH = 3.8-5.5 to obtain relatively pure solutions of pre-purified acid from fluorine and sulphate.

Residual sulphates and fluorine are deposited with calcium ions as $CaSO_4$ va CaF_2 and iron and aluminium ions are deposited as $FePO_4$ and $AlPO_4$. The sediment is separated from the solution by decantation.


Results. The territory of the republic consists of calcium and magnesium carbonates that meet technological requirements of industrial production: calcite, limestone, dolomite and other local minerals are found in large quantities. In the process of extraction of phosphoric acid with sulphuric acid, the use of local carbonate raw material in fluoridation and desulphurization of extraction suspension is very efficient.

The results of the research are presented in Tables 1, 2 and 3, as well as in Figures 1, 2 and 3.

Discussions. Table 1 shows that when EPA is produced without adding calcium carbonate, 5.45% of all fluorine in phosphate is converted into a gas phase, 40.5% into phosphogypse and 54.05% of fluorine remains in EPA. The following reactions may occur when adding calcium carbonate to the extraction suspension:



Magnesium fluoride is relatively soluble in acids than calcium fluoride, reacting with strong acids, including sulphuric acid:



magnesium sulfate and hydrogen fluoride.

This process is complex because magnesium monophosphate and sulphate, which are well soluble in EPA, can react with calcium carbonate to form calcium sulphate monophosphate. However, magnesium carbonate also reacts with phosphoric acid to form magnesium monophosphate. This is confirmed by the fact that the amount of magnesium in the EPA remains constant at 0.80-0.82% (Table 1).

With the addition of calcium carbonate and the formation of calcium fluoride, the amount of fluorine released into the gas phase decreases from 5.45% to 4.11%, indicating that the bulk of it is released at the beginning of the process. When CaCO₃ is added to the decomposition process at a rate of 100-150%, the total conversion of fluorine to the gas phase and phosphogypsum is 86.6-90.9%. The fluoride content of EPA is 0.25-0.32%, which is 4.1-5.3 times less than in the absence of calcium carbonate.

table.1.

Effects of calcium carbonate norm on EPA chemical composition, gas phase and phosphogypso permeability of fluorine, as well as technological parameters of production of fluorinated and desulphurized EPA

Name the indicators	Calcium carbonate content for binding free fluorine in stoichiometry,%						
	-	60	80	100	120	140	150
Standard for calcium carbonate binding free H ₂ SO ₄ to stoichiometry,%	-	80	100	100	100	100	100
EPA chemical composition, heavy. %							
P ₂ O ₅	20,15	20,08	19,97	19,85	20,24	19,94	20,02
CaO	0,41	0,39	0,58	0,94	1,46	2,14	2,61
MgO	0,82	0,81	0,81	0,80	0,82	0,81	0,81
SO ₃	2,22	0,86	0,51	0,48	0,52	0,47	0,44
R ₂ O ₃	0,61	0,61	0,60	0,60	0,59	0,60	0,59
F	1,32	0,69	0,51	0,32	0,27	0,25	0,25
particulate matter	0,25	0,32	0,28	0,19	0,24	0,17	0,16
Fluorine conversion rate, %							
Phosphogypsum	40,5	68,4	74,1	82,5	85,7	86,6	86,8
gaseous phase	5,4	5,3	5,1	4,1	4,2	4,0	4,1
All	45,9	73,7	79,2	86,6	89,9	90,6	90,9
Technological parameters of production of fluorinated and sulfated EPA							
K _{p.} %	98,7	98,7	98,7	98,6	98,5	98,5	98,4
K _{sep.} %	95,8	95,7	95,5	95,5	95,6	95,5	95,5
K _{wash.} %	99,2	99,3	99,3	99,4	99,4	99,4	99,3
K _{prod.} %	95,0	95,0	94,8	94,9	95,0	94,9	94,8



The density of the porridge (ρ), g/sm ³ , 25°C	1,26	1,26	1,26	1,26	1,26	1,27	1,27
The stickiness of the porridge (η), spz, 25°C	3,31	3,48	3,58	3,61	3,66	3,70	3,72
Extraction porridge filtration rate, kg/m ² .s	810,11	809,07	808,20	807,41	806,85	806,60	806,46
Size of phosphogypsum crystals, μm	100x24, 120x20, 220x20, more 560x80, 400x80, 360x28 and partially 100x16, 80x60, 60x20						

When the CaCO₃ content in CaO is 100-120%, the EPA degree of fluorination is 75.4-80.5%, and the sulphating rate is 78.7-79.6% (figures 1 and 2). Figures show that adding more than 120% calcium carbonate to the amount of fluorine and sulphate in acid changes very little with the loss of fluoride and sulphate. The amount of fluorine remaining in EPA is 9.1-13.4% of the total phosphate. When the level of calcium carbonate in phosphate changes from 60 to 100%, the additional conversion of fluorine to phosphogypse is 27.9-42.0%. Increasing the level of calcium carbonate by 120-150% increases the conversion of fluorine to the solid phase by only 3.2-4.3%. Excess calcium carbonate from EPA is used in the deposition of fluorine to form calcium sulphate due to the presence of excess sulphuric acid and monocalcium phosphate due to its interaction with phosphoric acid. The data in Table 2 show that the SO₃ content decreased from 2.22% to 0.44-0.52% and the calcium oxide content increased from 0.41% to 2.61%. The decomposition, separation, leaching and yield coefficients range from 60 to 150 per cent for fluorine binding, from 80 to 100 per cent for neutralizing the excess sulphuric acid for normal calcium carbonate 98.4 to 98.7 per cent and 95.5 to 95.8 per cent respectively. 99.2-99.4 per cent and 94.8-95.0 percent.

table 2

Technological parameters of production of fluorinated and sulphated EPA with WRPC

Name the indicators	WRPC standard for binding free fluorine relative to stoichiometry,%						
	-	60	80	100	120	140	150
MOFK standard for binding free H ₂ SO ₄ to stoichiometry,%	-	80	100	100	100	100	100
Chemical composition of EFK, heavy. %							
P ₂ O ₅	20,15	20,87	21,28	21,13	21,71	21,81	21,89
CaO	0,41	1,04	1,17	1,26	1,55	1,94	2,15
MgO	0,82	0,85	0,86	0,85	0,88	0,89	0,88
SO ₃	2,22	0,90	0,61	0,47	0,48	0,48	0,48
R ₂ O ₃	0,61	0,63	0,64	0,63	0,65	0,66	0,66
F	1,32	0,74	0,56	0,36	0,30	0,31	0,31
particulate matter	0,25	0,34	0,31	0,25	0,27	0,28	0,19

The filtration rate of phosphogypsum is relatively high, ranging from 806.46 to 809.07 kg/m²·s for dry matter.

Table 2 and figures 1 and 2 show the results of the fluorination and desulphurization of EPA at the Central Kyzylkum WRPC.

Unlike the use of calcium carbonate in acid cleaning, the use of UCFC increases the amount of P₂O₅ in EPA from 19.85-20.15% to 20.15-21.89%, the formation of calcium fluoride is 120-150% and the formation of calcium sulphate. The amount of CaO in the acid is 1.26-2.15%, the amount of MgO and SO₃ is practically unchanged and the amount of fluorine in the acid is reduced to 0.31%.

Figures 1 and 2 present comparative data on fluoridation and desulphurization levels of calcium carbonate and WRPC. The figures show that with a normal calcium carbonate of 100-120% the fluorination level is 2.2-2.4% higher than that of WRPC and the sulphate level is 1.7-2.3% lower.

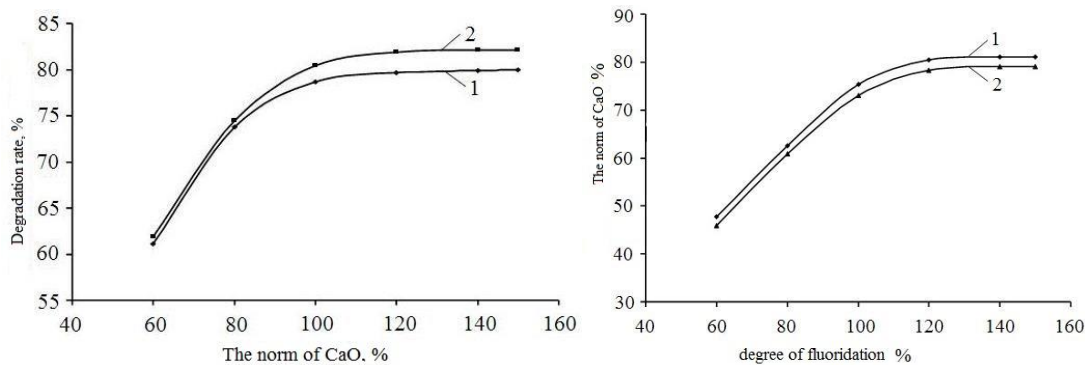


Figure.1. Effects of calcium carbonate (1) and UCFC (2) levels on fluorination

Figure.2. Effects of calcium carbonate (1) and UCFC (2) levels on sulphate levels.

Based on the research, a material balance of purification of fluorine and sulphate in the production of extractive phosphate acid from washed phosphate concentrate of Central Kyzylkum was developed (Figure 3). Production of high-quality concentrated phosphorus fertilizers based on fluoride and non-sulphate EPA is ensured.

The technology of EPA production from fluorine and sulphates has been tested in the industrial production of OAO «Ammophos-Maxam» and a prototype of high-quality mineral fertilizer of ammophos is made from this acid. The difference between the cost of Class I and Class I is 94,000 sums per ton. The production of 100 thousand tons of fertilizer will produce an economic effect of 9.4 billion sum.



inc.

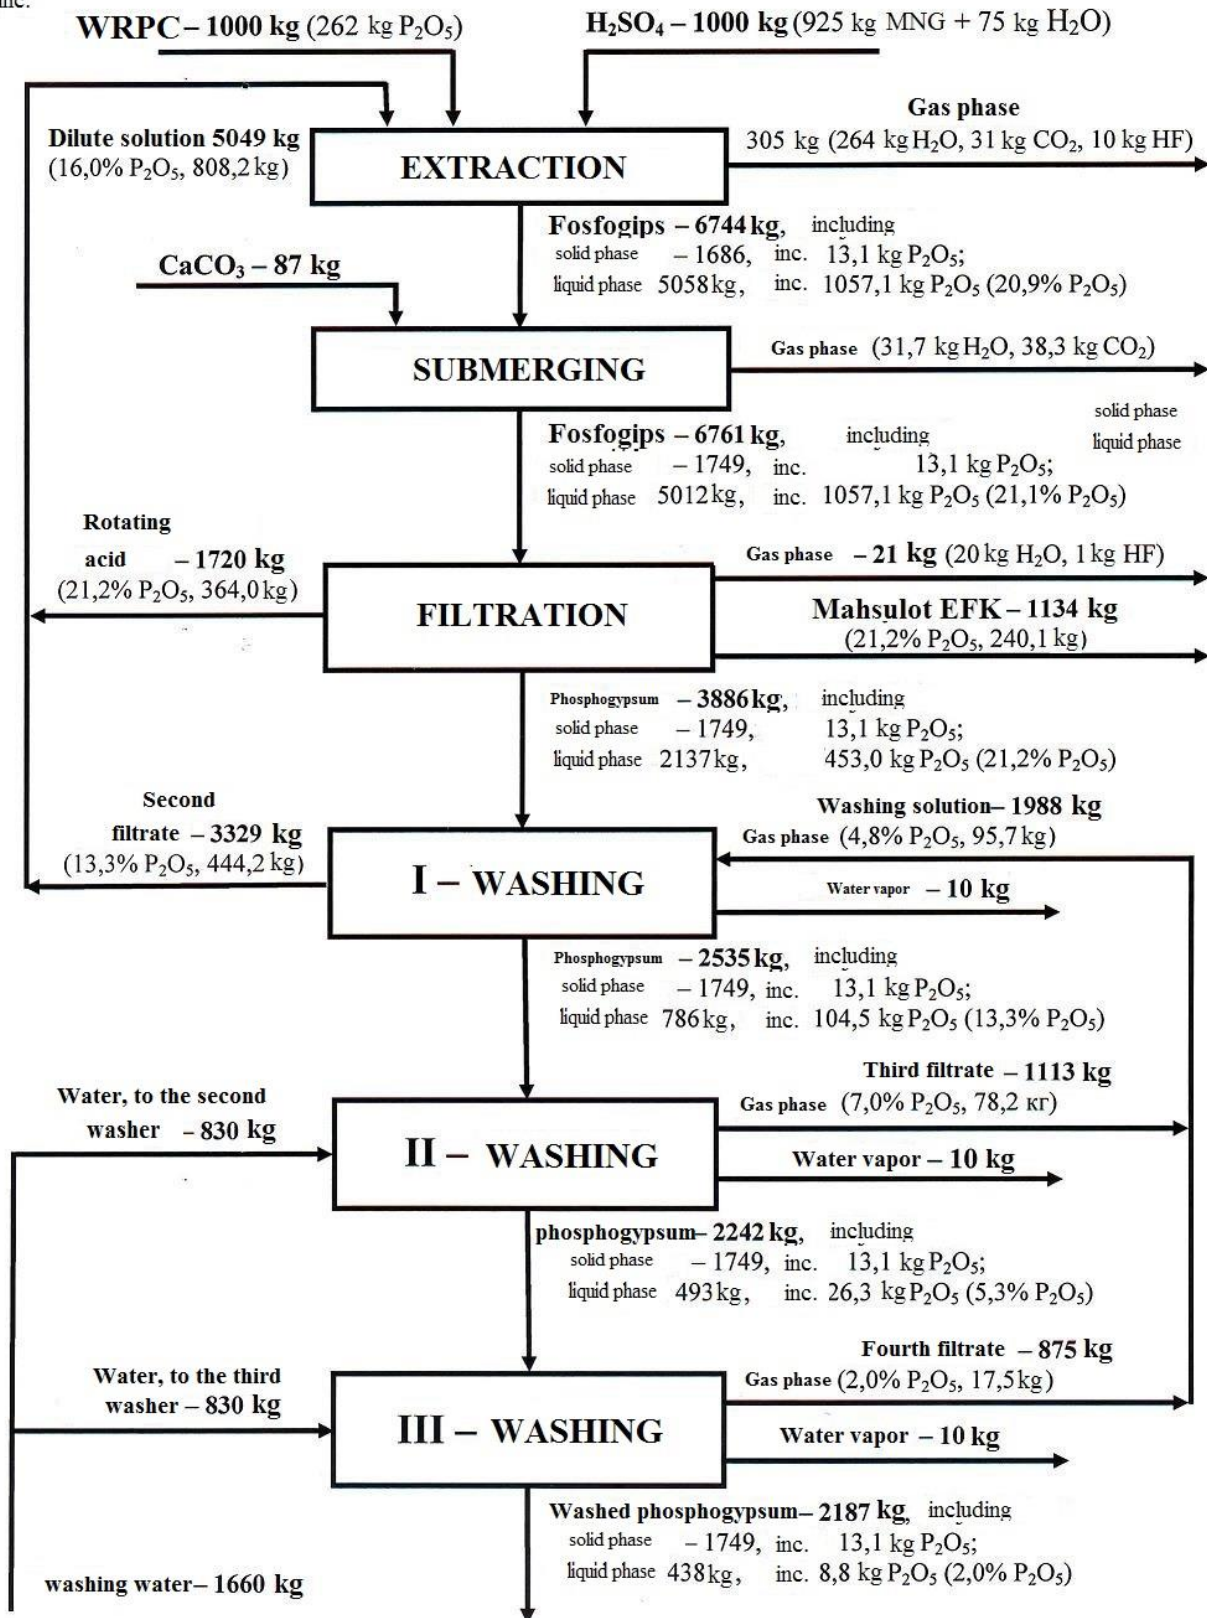


Figure 3. Material balance of production of EPA purified from fluorine and sulphate using carbonate feedstock



Adding calcium carbonate to the extraction solution solves three problems: partial discoloration and sulphate of extracted acid and calcium ion enrichment.

Ammonia with gaseous ammonia up to pH = 3.8-5.5 to obtain relatively pure solutions of pre-purified acid from fluorine and sulphate. Residual sulphates and fluorine are deposited with calcium ions as CaSO_4 and CaF_2 , and iron and aluminium ions are deposited as FePO_4 and AlPO_4 . The sediment is separated from the solution by decantation.

Table 3 shows the influence of ammonium level (pH) on the chemical composition of water-soluble ammonium phosphates.

table 3

Effects of ammonia level on the chemical composition of ammonium phosphates

pH	Chemical composition of ammonium phosphates, w. %				
	P ₂ O ₅	N	F	SO ₃	H ₂ O
3,8	56,91	11,54	0,11	0,24	1,43
4,5	58,63	12,83	0,03	0,08	2,54
5,2	59,95	13,71	0,01	0,04	2,18
5,3	58,81	14,03	0,01	0,03	2,27
5,5	57,48	14,21	0,01	0,02	1,34

When pH increased from 3.8% to 5.5, fluorine content decreased from 0.11% to 0.01% and sulphate from 0.24% to 0.02%, while P₂O₅ and nitrogen were 56.91% and 11.54% to 59.95% and 14.21%, respectively.

High-quality water-soluble ammonium phosphates can be obtained by partially purifying phosphoric acid during extraction and complete purification by extracting phosphoric acid with ammonia. The result is a simultaneous reduction of fluorine content from 0.11% to 0.01% and sulphates from 0.24% to 0.02% containing 56.91-59.95% P₂O₅ and 14.21-11.54%. A product with N was produced.

Conclusion. Studies have shown that simultaneous fluorination and desulphurization of EPA based on Central Kyzylkum phosphate can be achieved by adding calcium carbonate or WRPC to the extraction sludge. The optimal calcium carbonate and UFC levels are 100-120% for calcium fluoride and 100% for calcium sulphate. The sulphate content decreases from 2.22% to 0.44-0.48%, the fluorine content decreases from 1.32% to 0.25-0.30%, the rate of conversion of fluorine to the gas phase by extraction from 5.4% to 4%, and the rate of transition to phosphogypse increases from 40.5% to 82.5% to 85.7%. After purification from fluorine and sulphate, ammonium contains not more than 0.8-1.0% fluorine and more than 52.0% P₂O₅. The net profit from the conversion of refined EPA to ammonium is not less than 52.0% of P₂O₅ in the amount of 100,000 tonnes. Tonnes is 9.4 billion Sum.

High-quality water-soluble ammonium phosphates can be obtained from Central Kyzylkum phosphates by partial purification by phosphoric acid extraction and complete purification by the extraction of phosphoric acid with ammonia. The result is a simultaneous reduction of fluorine from 0.11% to 0.01% and sulfates from 0.24% to 0.02%, containing 56.91-59.95% P₂O₅ and 14.21-11.54%. A product with N was obtained. The products are integrated



water-soluble nitrogen-phosphorus fertilizers that are used to grow crops by drip irrigation and hydroponics.

References:

1. Najmiddinov, R., Shamshidinov, I., Qodirova, G., Nishonov, A., & Sayfiddinov, O. (2022). Марказий Қизилқум фосфоритлари асосидаги экстракцион фосфат кислотадан юқори сифатли аммоний фосфатлари олиш. *Science and innovation*, 1(A4), 150-160.
2. Юсупов, И., Зокиров, М., & Сайфиддинов, О. (2022, October). БИОГОМУС ЎҒИТЛАРИ.
3. БИОГОМУСНИНГ ХОССАЛАРИ ВА ҚЎЛЛАНИЛИШИ. In *Международная конференция академических наук* (Vol. 1, No. 29, pp. 17-24).
4. Сайфиддинов, О., Ғойипов, А., & Рахмонов, Д. (2022). Композицион фенолформальдегид смолаларини термик хоссаларини ўрганиш. *Zamonaviy dunyoda innovatsion tadqiqotlar: Nazariya va amaliyot*, 1(23), 99-102.
5. Турсунбоев, Х., & Сайфиддинов, О. (2022). ИСПОЛЬЗОВАНИЕ ИННОВАЦИОННЫХ ТЕХНОЛОГИЙ В ОБУЧЕНИИ СТУДЕНТОВ НЕХИМИЧЕСКИХ НАПРАВЛЕНИЙ. *Zamonaviy dunyoda innovatsion tadqiqotlar: Nazariya va amaliyot*, 1(28), 434-438.
6. Юлдашева, Н., Сиддиқова, Ў., Тўхтасунова, М., & Сайфиддинов, О. (2023). ГАЗОВЫЕ ДАТЧИКИ ДЛЯ ПРИРОДНОГО И ГОРЯЧЕГО ГАЗА ХИМИЧЕСКИЕ ДАТЧИКИ ЗОЛ-ГЕЛЬ СИНТЕЗ НАНОКОМПОЗИТНЫХ ПЛЕНОК. *Естественные науки в современном мире: теоретические и практические исследования*, 2(4), 18-20.
7. Eminov, A., Jumanov, Y. U., Umarov, F., & Sayfiddinov, O. (2022). PROSPECTS FOR THE USE OF KAOLINS OF UZBEKISTAN. *Science and Innovation*, 1(6), 367-373.
8. Сайфиддинов, О. (2023). СОДЕРЖАЩИЕ ЦЕНТРАЛЬНЫЕ КРАСНЫЕ ФОСФОРИТЫ КОНЦЕНТРИРОВАННЫЙ ФОСФОР С КАЛЬЦИЕМ И МАГНИЕМ ПОЛУЧЕНИЕ ПРОСТЫХ УДОБРЕНИЙ. *Евразийский журнал академических исследований*, 3(7), 213-215.
9. Najmiddinov, R., Shamshidinov, I., Kodirova, G., & Sayfiddinov, O. (2023). MARKAZIY QIZILQUM FOSFORITLARI ASOSIDA FOSFOR KISLOTANI KALSIY KARBONATI BILAN EKSTRAKTSIYA VA BITTA FOSFORLI O'G'ITDAN OLISH JARAYONDA TOZALASH. *Tsentrlnoaziatskiy jurnal akademicheskix issledovaniy*, 1 (2), 47-57.
10. Eminov, A. M., Sh, U. F., & Sayfiddinov, O. O. (2023). Mahalliy kaolinlar asosida qurilish keramikasi materiallari olish istiqbollari. *Строительство и образование*, 1(3), 22-27.
11. Сайфиддинов, О., & Усканбеков, О. (2022). НАНО-ЗАРРАЧАЛАРНИНГ ХОССАЛАРИИ ЎҒАНИШ. *Инновационные исследования в современном мире: теория и практика*, 1(28), 18-22